

Electrodeposition of Iron from Molten Mixed Chloride/Fluoride Electrolytes

Geir Martin Haarberg^a, Eirin Kvalheim^a, Sverre Rolseth^b, Tsuyoshi Murakami^c,
Stanislaw Pietrzyk^d, and Shulan Wang^e

^aDepartment of Materials Technology, Norwegian University of Science and Technology,
NO-7491 Trondheim, Norway

^bSINTEF Materials and Chemistry, NO-7465 Trondheim, Norway

^cInstitute of Advanced Energy, Kyoto University, Japan

^dDepartment of Metallurgy of Non-Ferrous Metals, AGH University of Science and
Technology, Krakow, Poland

^eDepartment of Chemistry, Northeastern University, Shenyang 110004, China

The electrochemical behavior of dissolved Fe₂O₃ and the electrodeposition of iron in molten CaCl₂-CaF₂ (80-20 mol %) and other mixed chloride/fluoride electrolytes was studied at 827 °C and 890 °C by cyclic voltammetry, chronoamperometry and galvanostatic electrolysis, and deposits were characterized by XRD and SEM. Pure iron was obtained in these melts at current efficiencies greater than 90 %. High cathodic current densities (~0.5 A cm⁻²) were achieved by using a rotating cathode. The work is related to studies of the possible development of new processes for the production of iron and steel with large reductions of CO₂ emissions.

Introduction

The production of iron and steel causes large emissions of CO₂. Iron electrowinning in molten salts with dissolved Fe₂O₃ using an inert oxygen evolving anode is an alternative process to reduce or eliminate the formation of CO₂.

The earliest work on iron deposition was reported in 1944 by Andrieux and Weiss (1). Electrolysis experiments were carried out in sodium peroxide, sodium carbonate and sodium metaborate using iron electrode at 450-500 °C and 10-25 A. Instead of iron deposits, sodium and magnetite were deposited on the cathode. In the 1960s Zulkiewitz et al. (2, 3) used eutectic KCl-LiCl-FeCl₂·4H₂O at 150-225 °C, and obtained iron deposits. However, due to the dehydration of the melt, FeCl₂ sublimation and decomposition occurred. In their further study, LiCl was replaced by NaCl, which made the iron crystal size drop from 2-3 mm to 1-10 μm (4). Great efforts on the electrodeposition of iron from molten salts were made in the former Soviet Union for powder metallurgy applications, but the process was never commercialized. A. B. Suchkov et al. (5) tested the electrorefining of scrap iron and pig iron. Dendritic iron was produced in NaCl-FeCl₂ (10 wt %) melt at 850-900 °C and the current efficiency decreased rapidly due to the dendritic growth of the deposit. By increasing the iron concentration of electrolytes and decreasing starting current, iron grains in the cathode grew coarsely (6). Electrorefining of iron from molten NaCl-KCl-FeCl₂-MgCl₂ and electrowinning of iron from molten NaF-KF, NaF-KF-NaCl, NaCl-KCl-FeCl₂, NaCl-KCl-FeCl₂-MgCl₂ and NaCl-KCl-Na₄P₂O₇-K₄P₂O₇ was also tried at 900-950 °C (7, 8). In NaF-KF electrolyte iron deposit grains were about 0.5 – 0.1 mm and decreased with the addition of NaCl. The iron

deposits in the phosphate containing electrolyte were contaminated by phosphorus and the phosphorus content in the iron deposit was about 1.5% P, and no iron was deposited in NaCl-KCl-FeCl₂ electrolyte. In 1987, Demidov et al (9) studied the reduction of Fe₂O₃ and Fe₃O₄ in LiCl-KCl eutectic electrolyte by the cyclic voltammetry method, and assumed the reduction Fe₃O₄ occurred in three steps. Haarberg et al. (10, 11) studied the electrochemistry of Fe₂O₃ dissolved in several chloride and fluoride containing electrolytes, and found that the solubility of Fe₂O₃ in CaCl₂-NaCl melts was greatly enhanced upon additions of AlCl₃, AlF₃ or MgCl₂, but a divalent iron species was produced by an exchange reaction between hematite and aluminium chloride, and chlorine gas was evolved. In molten fluorides and mixed fluoride/chloride electrolytes CaCl₂-KF (15-85 mol %), CaCl₂-KF-NaF (7-39-54 mol %), KF-NaF (50-50 mol %) and LiF-KF-NaF (46.4-42.1-11.5 mol %), the exchange reaction was avoided. However, the solubility of hematite was more limited in the absence of an acidic substance such as AlCl₃ (10). In a novel process of producing titanium, Chen et al (12) used CaCl₂ as the main electrolyte due to the high solubility of CaO in the melt. In the present work, the electrochemistry of iron in CaCl₂-CaF₂ (80-20 mol %) was studied.

Experimental

CaCl₂ and CaF₂ of analytical quality were dried in air for 48 h and kept and weighed in a glove box to avoid contact with moisture. An air tight cell with radiation shields of aluminum oxide, and carbon crucibles (75 mm × 60 mm in diameter, 117 mm in height) were used in the experiments. Argon gas was circulated through the cell to maintain an air-free atmosphere. The temperature inside the furnace was measured with a thermocouple of S type (Pt-Pt/10%Rh) placed in a closed aluminium tube. The salt (150 g) was heated to 200 °C and kept at this temperature overnight, and then heated to 800 °C. The electrochemical techniques of cyclic voltammetry and chronoamperometry were used to study the behavior of dissolved iron species. A molybdenum wire (2mm in diameter) and a platinum wire (1 mm in diameter) were used as the reference and the working electrodes, respectively. A magnetite rod (anode no: 1-2005, made at SINTEF Material and Chemistry, 100 % magnetite, axially pressed, sintered under argon atmosphere at 950 °C for two hours, with electrical conductivity at room temperature of 366 Ω⁻¹m⁻¹ and size 25 mm in diameter, 60 mm in length) was used as the counter electrode in the electrolysis experiments and a carbon rod (10 mm in diameter, 200 mm in length) was used as the counter electrode in the electrochemical measurements. The electrodeposition of iron was performed by the galvanostatic electrolysis method and the iron deposits were washed in distilled water bubbled with argon, dried in air and characterized by XRD and SEM.

Results and Discussion

Several different electrolytes were tested. It was found that mixtures of chloride and fluoride salts were beneficial. In this paper only results obtained in molten CaCl₂-CaF₂ are presented.

CaCl₂-CaF₂ Melt

The electrochemical behavior of dissolved iron species Fe(III) in molten CaCl₂-CaF₂ (80-20 mol %) was studied by linear cyclic voltammetry and chronoamperometry in

greater detail as a function of Fe_2O_3 concentration. The cyclic voltammograms on a molybdenum working electrode with 0.5 mol % Fe_2O_3 concentration at different sweep rates have the quite typical shape for a metal deposition reaction (as shown in Figure 1) with steep anodic stripping peaks. No apparent cathodic background current was observed in the cyclic voltammograms. The deposition of iron takes place directly from Fe(III) species.

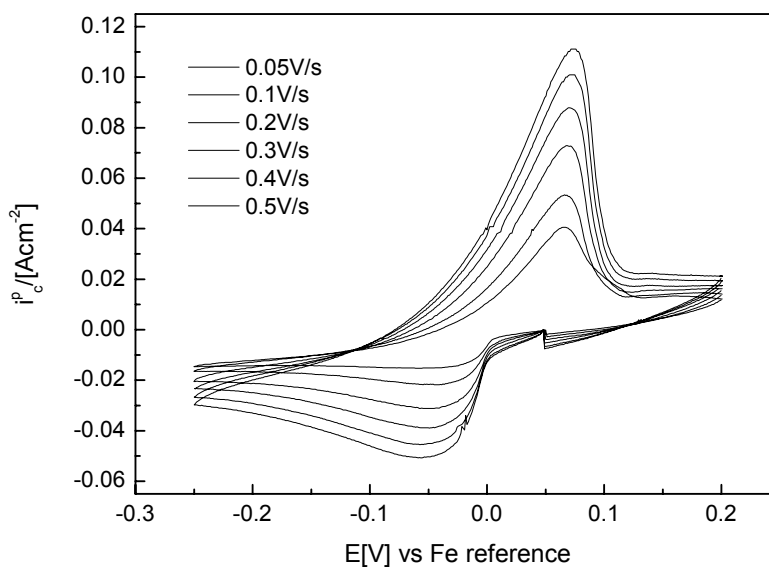


Figure 1. Cyclic voltammograms at a molybdenum working electrode in $\text{CaCl}_2\text{-CaF}_2$ (80-20 mol%) with addition of 0.5 mol % Fe_2O_3 , 827 °C.

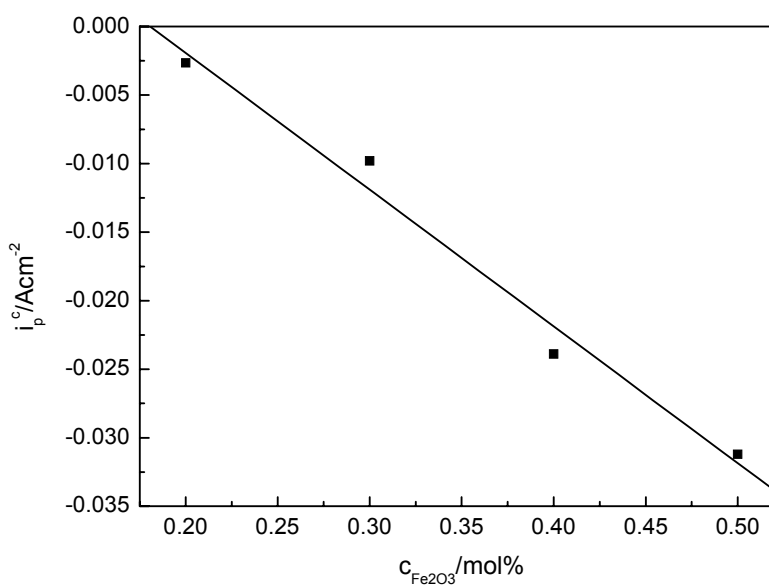


Figure 2. Voltammetric peak current density versus Fe_2O_3 concentration in $\text{CaCl}_2\text{-CaF}_2$ (80-20 mol %) with 0.2 V/s scan rate, 827 °C.

Figure 2 shows the cathodic peak current densities measured at different Fe_2O_3 concentrations in the electrolyte $\text{CaCl}_2\text{-CaF}_2$ (80-20 mol %). The current density for a diffusion controlled reaction is proportional to concentration, hence the current density plotted as a function of concentration should show a linear relationship if the iron deposition reaction is diffusion controlled. From Figure 2, it can be seen that the current densities measured in the electrolyte $\text{CaCl}_2\text{-CaF}_2$ (80-20 mol %) follow the linear relationship quite well. The cathodic peak current density increased with increasing Fe_2O_3 concentration, and the results obtained suggest that the solubility of Fe_2O_3 in molten $\text{CaCl}_2\text{-CaF}_2$ (80-20 mol %) is at least 0.5 mol % at 827 °C.

The cathodic peak current density was plotted as a function of the square root of the sweep rate for $\text{CaCl}_2\text{-CaF}_2$ (80-20 mol %), and very good linear fits were obtained. From the slope of the straight line the diffusion coefficient of the Fe(III) iron species in $\text{CaCl}_2\text{-CaF}_2$ (80-20 mol %) at 827 °C was calculated to be $3.0 \times 10^{-5} \text{ cm}^2\text{s}^{-1}$. Chronoamperometry did not reveal any signs of nucleation or phase formation.

Iron electrolysis was performed in $\text{CaCl}_2\text{-CaF}_2$ (80-20 mol %), with addition of 1 mol % Fe_2O_3 using a rotating iron cathode (210 rpm/min) at 890 °C by the galvanostatic electrolysis method. Pure iron was obtained, as can be seen from the XRD pattern in Figure 3. The current efficiency with respect to iron was found to be 92 % in this experiment. Small amounts of Fe_3O_4 were found in the iron product, and this could be due to partial reduction of Fe_2O_3 by the carbon crucible. CaF_2 is difficult to dissolve in water and therefore some CaF_2 remained in the iron product and lowered the purity of iron.

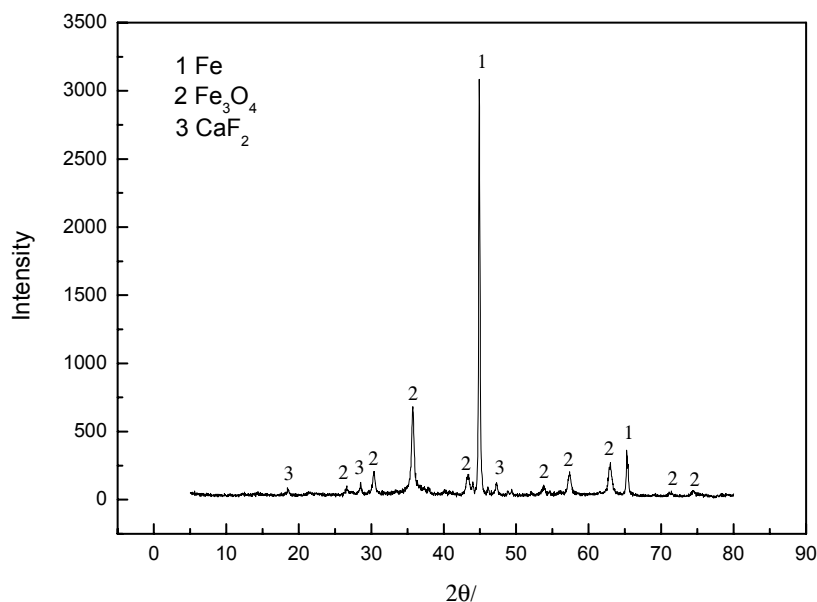


Figure 3. XRD pattern of iron deposit from $\text{CaCl}_2\text{-CaF}_2$ (80-20 mol %), 890 °C.

Conclusions

The electrochemical behavior of dissolved Fe₂O₃ in molten CaCl₂-CaF₂ (80-20 mol %) was studied at 827 °C and 890 °C by electrochemical techniques. Iron was found to be deposited from Fe(III) complexes; the diffusion coefficient of the Fe(III) species at 827 °C was determined by voltammetry to be 3.0×10^{-5} cm²/s in CaCl₂-CaF₂ (80-20 mol %). Pure iron was electrodeposited at current efficiencies greater than 90 %. The solubility of Fe₂O₃ in the melt was estimated to be about 0.5 mol %. The results are promising for the possibility of developing a new process for the production of iron.

Acknowledgments

This work was performed within the ULCOS project, contract no NMP2-CT-2004-515960.

References

1. L. Andrieux and G. Weiss, "Productions of electrolysis of molten salts with an iron anode", *Comptes Rendu*, **217**, 615 (1944).
2. S. Ziolkiewitz, "Preparation of iron from a molten eutectic KCl-LiCl+ FeCl₂.4H₂O", *Comptes Rendu*, **247**, 1604 (1958).
3. S. Ziolkiewitz and A. Rimsky, "Properties and characteristics of iron monocrystals produced by electrolysis of low temperature molten salts: The eutectic KCl-LiCl+ FeCl₂.4H₂O", *Comptes Rendu*, **247**, 1727 (1958).
4. C. Goillot and S. Ziolkiewitz, "Magnetic properties of iron in the molten state and of massive iron of very high purity obtained by molten salt electrolysis", *Comptes Rendu*, **252**, 879 (1961).
5. A.B. Suchkov, T.N. Ermakova and V.B. Akimenko, "Production of pure iron powder by electrolysis of fused salts", *Powder Metallurgy*, **6**, 1 (1968).
6. T.N. Ermakova, A.B. Suchkov and V.B. Akimenko, "On the grain size of iron powder which is produced by electrolysis of fused salts", *USSR Proc. Acad. Sci. Metals*, **6**, 63 (1968).
7. A.B. Suchkov, T.N. Ermakova, Z.A. Tubyshkina, A.L. Sozina and B.F. Kovalev, *USSR Authors Certificate*, No. 323463, C 22d 1/24, (1972).
8. A.B. Suchkov, T.N. Ermakova, L.V. Ryumina, Z. A. Tubyshkina, "On the production of iron powder by electrolysis of ore concentrates in fused salts: Direct iron production and powder metallurgy", *Metallurgiya*, No.1, 148 (1974).
9. A.I. Demidov, I.A. Simikov, A. G. Morachevskii and A. V. Klevtsov, "Anodic polarization of iron oxide in molten eutectic mixture of lithium and potassium chlorides", *Russ. J. Appl. Chem.*, **60**, 948 (1987).
10. G.M. Haarberg, O.S. Burheim, H. Karoliussen, E. Kvalheim, A.M. Martinez, T. Murakami, S. Pietrzyk and D.J. Zhao, "Middle temperature electrolysis for the production of iron in molten salts", Project report, Norwegian University of Science and Technology, Trondheim, Norway, March 2006.
11. G.M. Haarberg, E. Kvalheim, and S. Rolseth, "Electrochemical behaviour of dissolved iron species in molten salts", in *Molten Salts XIV*, R.A. Mantz et al, Editors, PV 2004-24, p. 890, The Electrochemical Society Proceedings Series, Pennington, NJ (2004).
12. G.Z. Chen, D.J. Fray and T.W. Farthing, *Nature*, **407**, 361 (2000).